



GPO PRICE \$ _____

CFSTI PRICE(S) \$ _____

Hard copy (HC) 1.00

Microfiche (MF) -50

ff 653 July 65

N 66-11672

(ACCESSION NUMBER)

(THRU)

(PAGES)

(CODE)

(NASA CR OR TMX OR AD NUMBER)

(CATEGORY)

EVALUATION PROGRAM
for
SECONDARY SPACECRAFT CELLS

ACCEPTANCE TEST
OF
SONOTONE CORPORATION
5.0 AMPERE-HOUR NICKEL CADMIUM CELLS

prepared for
GODDARD SPACE FLIGHT CENTER

CONTRACT W11,252B



QUALITY EVALUATION LABORATORY
NAD CRANE, INDIANA

QUALITY EVALUATION LABORATORY
UNITED STATES NAVAL AMMUNITION DEPOT
CRANE, INDIANA

EVALUATION PROGRAM
FOR
SECONDARY SPACECRAFT CELLS

ACCEPTANCE TEST
OF
SONOTONE CORPORATION
5.0 AMPERE-HOUR NICKEL CADMIUM CELLS

QE/C 65-583

2 SEPTEMBER 1965

THIS REPORT IS LIMITED TO GOVERNMENT AGENCIES.
OTHER REQUESTS FOR COPIES SHOULD BE MADE TO:
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION
GODDARD SPACE FLIGHT CENTER (CODE 636.2)
GREENBELT, MARYLAND 20771

PREPARED UNDER THE DIRECTION OF

E. C. Bruess

E. C. BRUESS
Manager, Electrochemical
Power Sources Branch

APPROVED BY

E. R. PETTEBONE
COMMANDING OFFICER

W. Yeager
W. YEAGER
By direction

Enclosure (1)

REPORT BRIEF

SONOTONE FIVE AMPERE-HOUR NICKEL CADMIUM

SECONDARY SPACECRAFT CELLS

- Ref: (a) National Aeronautics and Space Administration Purchase Order Number W11,252B
(b) NASA ltr BRA/VBK/pad of 25 September 1961 w/BUWEPS first end FQ-1:WSK of 2 October 1961 to CO NAD Crane
(c) Preliminary Work Statement for Battery Evaluation Program of 25 August 1961

I. TEST ASSIGNMENT BRIEF.

A. In compliance with references (a) and (b), evaluation of Sonotone Corporation five ampere-hour nickel cadmium secondary spacecraft cells was begun according to the program outline of reference (c).

B. The object of this evaluation program is to gather specific information concerning secondary spacecraft cells. Information concerning performance characteristics and limitations, including cycle life under various electrical and environmental conditions, will be of interest to power systems designers and users. Cell weaknesses, including cause of failure of present designs, will be of interest to suppliers as a guide to product improvement.

C. Forty cells were purchased from Sonotone Corporation, Elmsford, New York by National Aeronautics and Space Administration (NASA). These cells are rated at five ampere-hours by the manufacturer and are similar to those used in the Tiros satellite program.

II. CONCLUSIONS.

A. From the results of this test, it can be concluded that:

1. The ceramic seals of these cells manufactured by Sonotone Corporation are satisfactory as evidenced by no leakers out of the 40 cells tested.

2. The capacity of the cells was in the acceptable range of 5.05 to 6.80 ampere-hours to 1.00 volt.

III. RECOMMENDATIONS.

A. It is recommended that these Sonotone Corporation 5.0 ampere-hour cells be accepted on the basis of the acceptance test results.

RESULTS OF ACCEPTANCE TESTS
OF
FIVE AMPERE-HOUR NICKEL CADMIUM SECONDARY SPACECRAFT CELLS
MANUFACTURED BY
SONOTONE CORPORATION

I. INTRODUCTION.

A. On 27 June 1965, this activity began acceptance tests on 40 cells. These tests were completed on 30 July 1965.

II. TEST CONDITIONS.

A. All acceptance tests were performed at an ambient temperature between 23° C and 27° C at existing relative humidity and atmospheric pressure, and consisted of the following:

1. Phenolphthalein Leak Test.
2. Capacity Test.
3. Cell Short Test.
4. Immersion Seal Test.
5. Overcharge Test.
6. Internal Resistance Test.
7. Immersion Seal Test.

B. All charging and discharging was done at constant current (\pm 5 percent). Cells were charged in series but were discharged individually.

III. CELL IDENTIFICATION AND DESCRIPTION.

A. The cells were identified by the manufacturer's serial numbers which were from A2410 to A2481 although not consecutively.

B. The five ampere-hour "F" cell is cylindrical with an average diameter of 1.306 inches and an average overall length of 3.624 inches including the positive terminal. The average weight was 263.3 grams. Figure 1 is a photograph of a Sonotone Corporation five ampere-hour "F" cell.

C. The cell container or can, and the cell cover are made of cold rolled steel. A stainless steel tab, welded to the cover, serves as contact for the negative terminal. The positive terminal is solder type extension of the positive plate tab through the center of the cover. The positive terminal is insulated from the "negative" cover by a ceramic seal. Two crimp rings, about 1/32 inch deep, are located about 7/8 inch from each end of the cell. These evidently tighten the element to withstand vibration.

D. These cells, rated by the manufacturer at five ampere-hours, were supplied in a partially discharged condition and will be tested with the stabistor charge control principle.

IV. TEST PROCEDURE AND RESULTS.

A. Phenolphthalein Leak Test:

1. The phenolphthalein leak test is a determination of the condition of the welds and ceramic seal on receipt of the cells. The test was performed with a phenolphthalein spray indicator solution of one-half of one percent concentration.

2. There were no signs of leakage on any of the 40 cells subjected to the leak test.

B. Capacity Test:

1. The capacity test is a determination of the cell capacity at the $c/2$ discharge rate, where c is the manufacturer's rated capacity, to a cutoff voltage of 1.00 volt per cell. The discharge was made after a 1-hour open circuit period following the 16-hour charge at the $c/10$ rate. A total of three capacity checks were made at this activity. The cells were discharged individually, but were recharged in series.

2. Since no capacity data was submitted by the manufacturer it was not possible to compare the manufacturer's capacity values with those of this activity. The individual cell capacities ranged from 5.05 to 6.80 ampere-hours for an average of 6.10 ampere-hours to 1.00 volt. The cell capacities are tabulated in Table I. Characteristic 2-hour rate discharge curves are shown in Figure 2.

C. Cell Short Test:

1. The cell short test is a means of detecting slight shorting conditions which may exist because of imperfections in the insulating materials, or damage to element in handling or assembly.

2. Following completion of the third capacity discharge test, each individual cell was loaded with a resistor of value giving a

c/1 to c/5 discharge rate and allowed to stand 16 hours with the resistor acting as a shorting device. At the end of 16 hours, the resistors were removed and the cells were placed on open circuit stand for 24 hours. Any cell whose voltage did not recover to 1.15 volts or higher after the 24-hour open circuit stand was rejected.

3. The open circuit cell voltages, 24 hours after removal of the shorting resistors, ranged from 1.20 to 1.25 volts for an average of 1.22 volts.

4. There were no rejects of any of the cells subjected to the cell short test. The voltage values for the 40 accepted cells are shown in Table I.

D. Immersion Seal Test:

1. The immersion seal test is a means of detecting leakage of a seal or weld. The test was performed before and after the overcharge sequence to determine the presence and cause of leaks.

2. The cells were placed under water in a bell jar container. A vacuum of 20 inches of mercury was held for 3 minutes. Cells discharging a steady stream of bubbles were considered rejects.

3. There were no rejects in the 40 cells subjected to the immersion seal test.

E. Overcharge Test:

1. The overcharge tests were performed to determine the steady state voltage at specified rates. The test specified a series of constant current charges at c/20, c/10 and c/5 rates, for a minimum of 48 hours at each charge rate or until the increase of the "on charge" voltage was less than 10 millivolts per day.

2. The cells were monitored hourly throughout the test. Charging was to be discontinued on cells which exceeded 1.50 volts while on charge. There was no need to remove any cells from the charging sequence.

3. The steady state voltage of each cell at the end of each 48-hour charge rate test is shown in Table I. Characteristic overcharge voltage curves are shown in Figure 3.

F. Internal Resistance Test:

1. This test was performed to determine the internal resistance of the cells.

2. At the completion of the overcharge test; the cells were returned to the $c/20$ charging rate and given a short pulse (5 - 10 seconds) at a rate of c in amperes. The cell voltages, V_1 , immediately prior to the pulse; and V_2 , 5 milliseconds after the pulse, were read on a suitable recording instrument. A CEC high speed oscillograph recorder (28.8 inches of tape per second) was used. The internal resistance of the cell in ohms was calculated according to the following formula:

$$R = \frac{V_2 - V_1}{I_c - I_c/20}$$

V_1 and V_2 are in volts, I_c and $I_c/20$ are in amperes.

3. The internal resistance value for each cell is shown in Table I. The values range from 4.21 milliohms to 8.42 milliohms.

TABLE I

CELL NUMBER	DIAMETER (INCHES)	LENGTH (INCHES)	WEIGHT (GRAMS)	CAPACITY TEST (A.H.)	CAPACITY TEST (A.H.)	CAPACITY TEST (A.H.)	CELL SHORT TEST (VOLTS)	IMMERSION SEAL TEST	OVERCHARGE C/20 (VOLTS)	OVERCHARGE C/10 (VOLTS)	OVERCHARGE C/5 (VOLTS)	INTERNAL RESISTANCE (MILLIOHMS)	IMMERSION SEAL TEST
A2410	1.307	3.644	240.6	5.92	5.20	4.68	1.21	O.K.	1.41	1.41	1.40	6.32	O.K.
A2411	1.300	3.648	229.1	5.13	5.00	5.00	1.24	O.K.	1.45	1.48	1.50	6.32	O.K.
A2413	1.300	3.620	235.3	6.20	5.88	6.28	1.24	O.K.	1.42	1.43	1.43	6.32	O.K.
A2414	1.300	3.625	236.5	6.18	5.88	6.04	1.24	O.K.	1.40	1.42	1.42	6.32	O.K.
A2415	1.304	3.640	236.9	6.18	6.00	5.75	1.23	O.K.	1.44	1.46	1.48	6.32	O.K.
A2419	1.310	3.631	237.4	6.04	5.55	5.75	1.22	O.K.	1.40	1.41	1.42	8.42	O.K.
A2420	1.308	3.627	237.3	6.38	6.00	6.16	1.22	O.K.	1.40	1.42	1.42	8.42	O.K.
A2422	1.304	3.655	243.9	6.13	5.30	4.50	1.25	O.K.	1.40	1.40	1.40	8.42	O.K.
A2423	1.304	3.615	235.1	5.70	5.33	5.46	1.23	O.K.	1.40	1.42	1.42	6.32	O.K.
A2424	1.300	3.650	233.2	5.30	5.00	5.28	1.24	O.K.	1.41	1.42	1.42	4.21	O.K.
A2426	1.305	3.625	233.0	5.92	5.45	5.08	1.22	O.K.	1.41	1.42	1.41	6.32	O.K.
A2427	1.303	3.629	237.0	6.00	5.05	4.38	1.25	O.K.	1.40	1.40	1.40	4.21	O.K.
A2430	1.300	3.650	235.2	5.93	5.08	4.78	1.24	O.K.	1.39	1.40	1.40	6.32	O.K.
A2431	1.312	3.635	241.2	5.63	5.13	5.35	1.23	O.K.	1.40	1.41	1.41	6.32	O.K.
A2432	1.303	3.615	238.8	6.38	6.20	5.95	1.22	O.K.	1.43	1.45	1.46	6.32	O.K.
A2434	1.300	3.625	237.1	5.93	5.25	5.50	1.24	O.K.	1.39	1.41	1.42	6.32	O.K.
A2435	1.300	3.585	234.3	6.43	6.25	6.46	1.23	O.K.	1.40	1.43	1.44	6.32	O.K.
A2437	1.312	3.638	240.0	6.05	5.93	5.80	1.23	O.K.	1.40	1.41	1.44	4.21	O.K.
A2442	1.304	3.615	236.4	6.33	6.30	6.05	1.21	O.K.	1.39	1.40	1.44	4.21	O.K.
A2443	1.305	3.600	237.0	5.00	5.05	4.75	1.23	O.K.	1.40	1.44	1.50	6.32	O.K.

TABLE I (Contd)

CELL NUMBER	DIAMETER (INCHES)	LENGTH (INCHES)	WEIGHT (GRAMS)	CAPACITY TEST (A.H.)	CAPACITY TEST (A.H.)	CAPACITY TEST (A.H.)	CELL SHORT TEST (VOLTS)	IMMERSION SEAL TEST	OVERCHARGE c/20 (VOLTS)	OVERCHARGE c/10 (VOLTS)	OVERCHARGE c/5 (VOLTS)	INTERNAL RESISTANCE (MILLIOHMS)	IMMERSION SEAL TEST
A2444	1.308	3.605	232.4	6.20	6.05	5.70	1.21	O.K.	1.40	1.42	1.46	6.32	O.K.
A2446	1.305	3.630	236.1	6.08	6.08	6.05	1.23	O.K.	1.44	1.48	1.50	4.21	O.K.
A2448	1.315	3.615	230.2	6.20	5.95	5.25	1.21	O.K.	1.40	1.40	1.43	6.32	O.K.
A2454	1.312	3.625	231.7	5.83	5.95	5.75	1.23	O.K.	1.40	1.40	1.42	6.32	O.K.
A2456	1.310	3.625	234.0	6.25	5.92	5.67	1.20	O.K.	1.41	1.42	1.42	6.32	O.K.
A2457	1.308	3.616	238.5	6.33	5.95	5.70	1.20	O.K.	1.43	1.44	1.43	6.32	O.K.
A2458	1.300	3.620	233.6	6.00	5.80	5.45	1.21	O.K.	1.39	1.39	1.41	6.32	O.K.
A2460	1.305	3.625	237.0	6.20	6.08	5.80	1.22	O.K.	1.39	1.40	1.43	8.42	O.K.
A2461	1.305	3.615	237.9	5.75	5.13	4.55	1.24	O.K.	1.39	1.40	1.41	8.42	O.K.
A2465	1.300	3.610	233.9	6.58	6.38	6.13	1.21	O.K.	1.40	1.42	1.47	6.32	O.K.
A2467	1.305	3.610	237.5	6.25	5.80	5.30	1.21	O.K.	1.39	1.39	1.41	8.42	O.K.
A2468	1.305	3.625	233.8	6.30	6.08	5.83	1.21	O.K.	1.39	1.42	1.50	6.32	O.K.
A2469	1.305	3.625	238.9	6.80	6.70	6.50	1.20	O.K.	1.43	1.44	1.46	4.21	O.K.
A2472	1.308	3.620	234.5	6.20	6.08	5.80	1.23	O.K.	1.39	1.41	1.45	6.32	O.K.
A2473	1.308	3.618	240.7	6.58	6.30	5.95	1.20	O.K.	1.42	1.42	1.42	6.32	O.K.
A2474	1.303	3.620	234.7	6.33	6.18	5.93	1.22	O.K.	1.39	1.41	1.45	8.42	O.K.
A2478	1.308	3.620	237.2	6.20	5.70	5.30	1.21	O.K.	1.41	1.41	1.41	6.32	O.K.
A2479	1.308	3.621	240.9	5.95	6.58	6.43	1.22	O.K.	1.42	1.42	1.43	6.32	O.K.
A2480	1.312	3.625	239.5	6.25	6.05	5.75	1.23	O.K.	1.42	1.44	1.49	6.32	O.K.
A2481	1.315	3.636	232.5	6.05	5.93	5.43	1.20	O.K.	1.43	1.45	1.46	6.23	O.K.



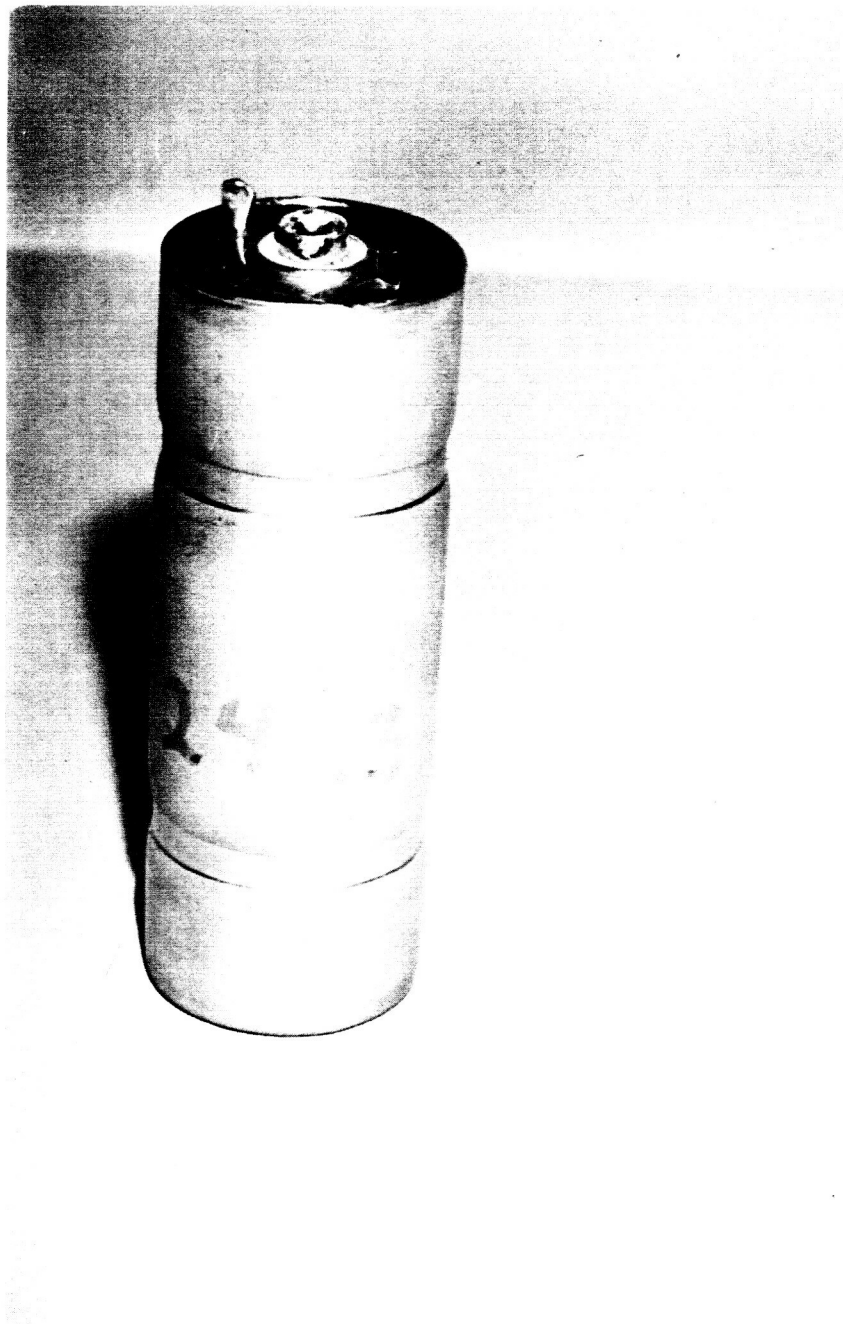


FIGURE 1

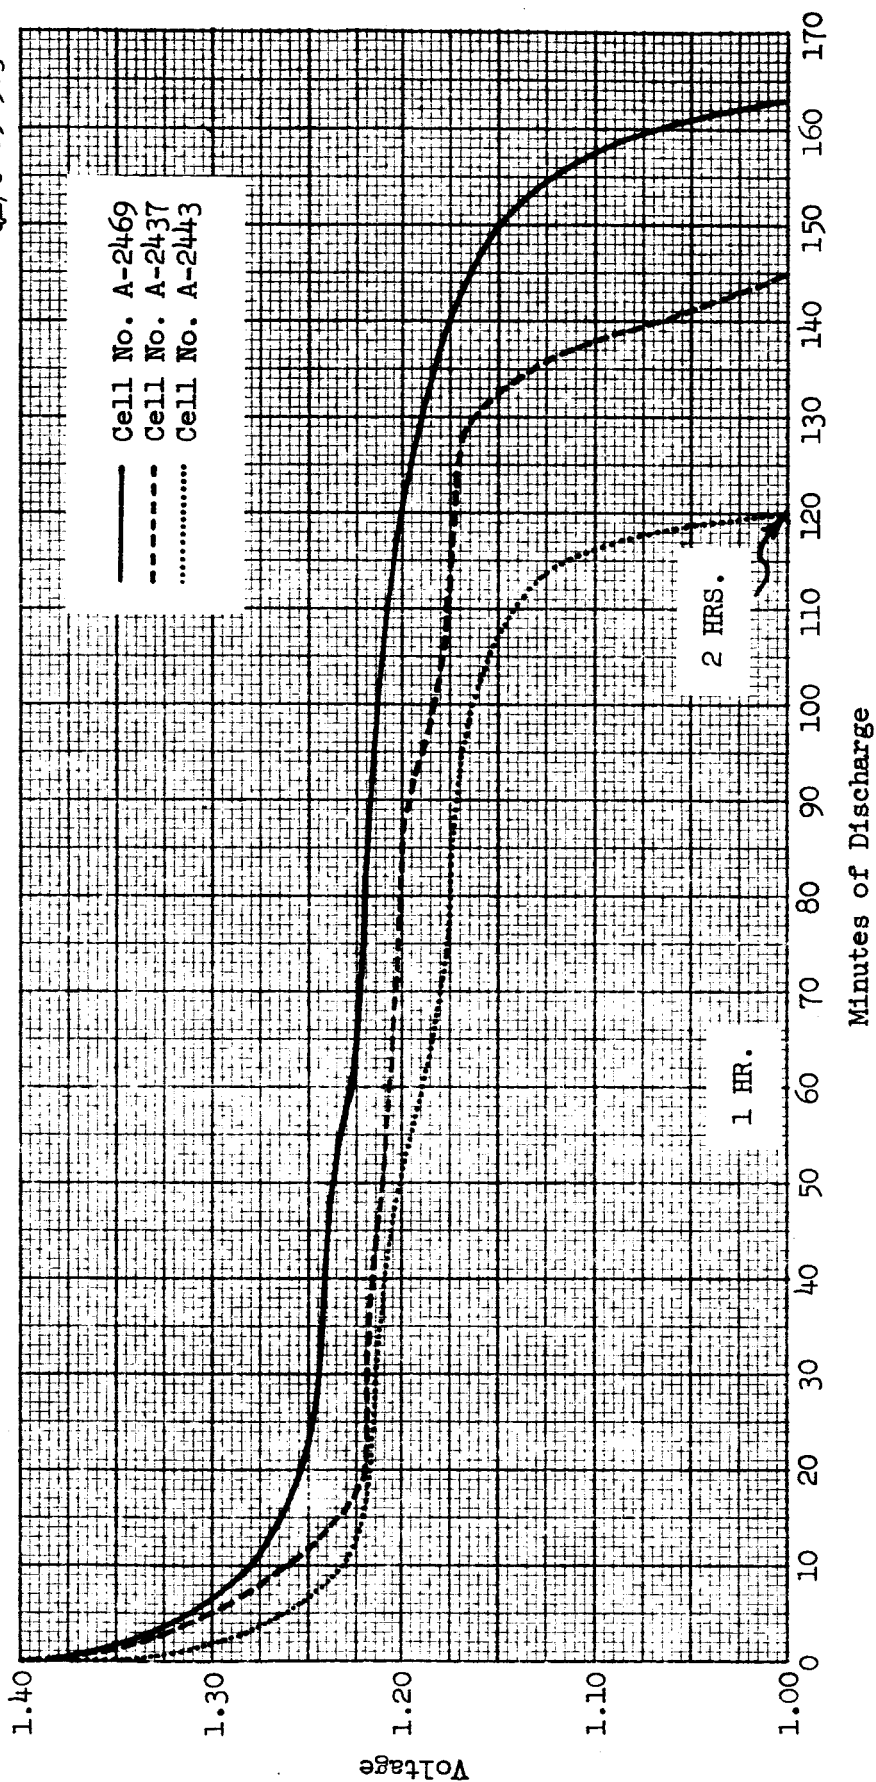

CHARACTERISTIC 2-HOUR RATE DISCHARGE CURVES

SONOTONE 5 AMPERE-HOUR NICKEL CADMIUM SEALED CELLS

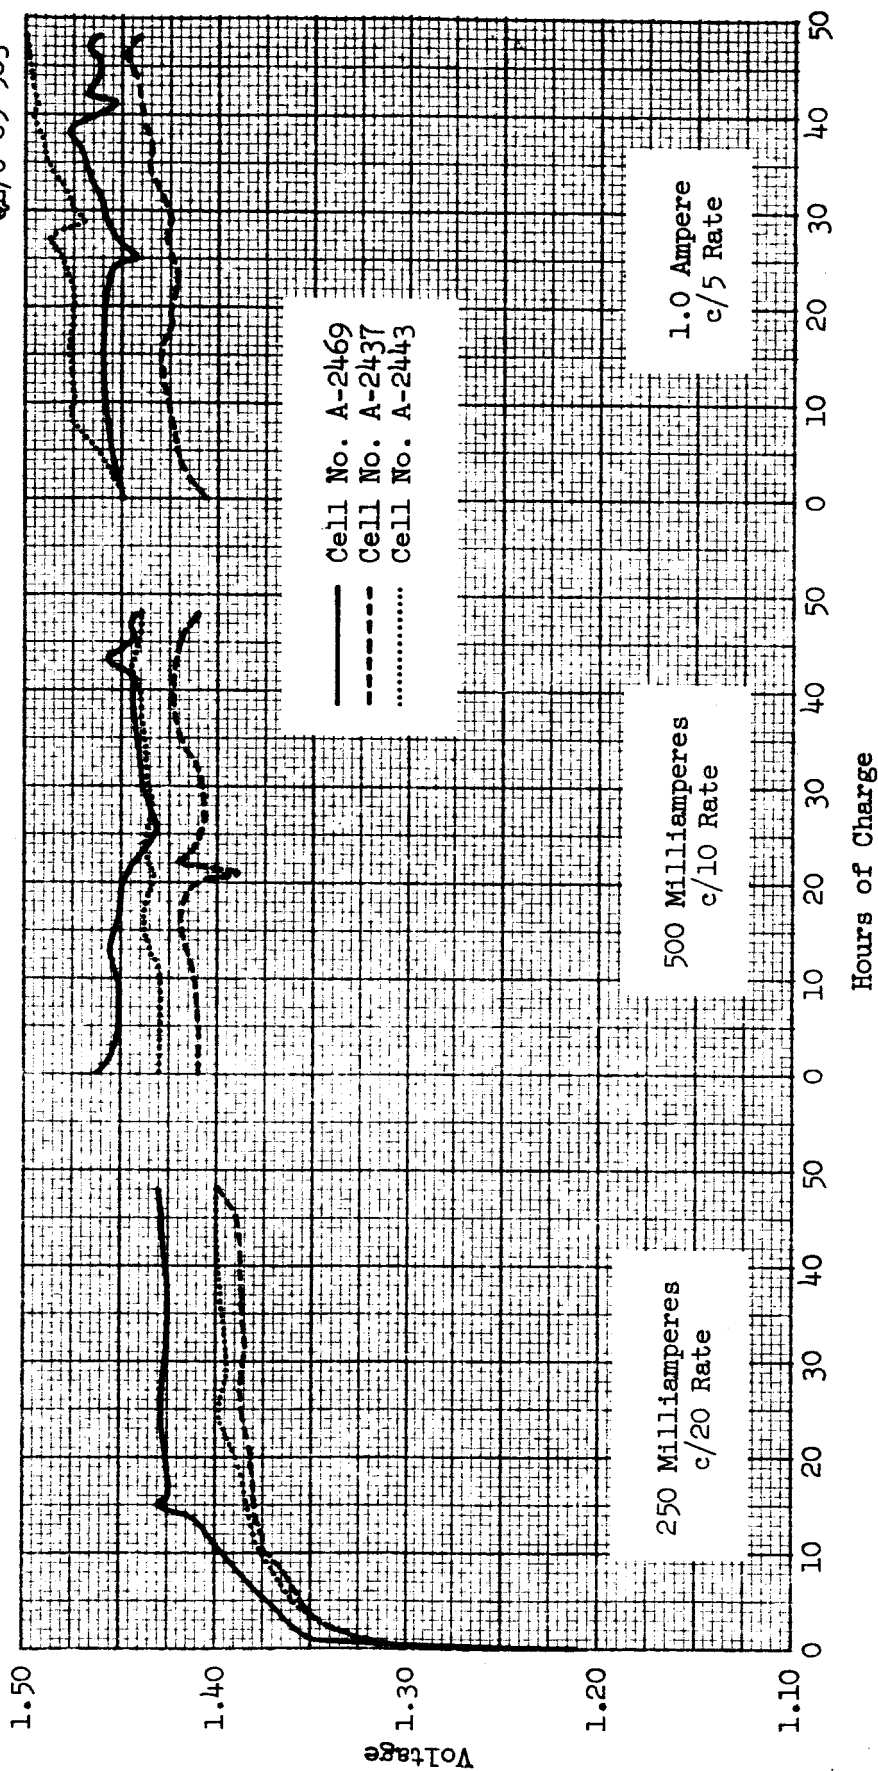

CHARACTERISTIC 48-HOUR OVERCHARGE CURVES

SONOTONE 5 AMPERE-HOUR NICKEL CADMIUM SEALED CELLS

FIGURE 3

DISTRIBUTION LIST

COPY NO.

- 1-4 National Aeronautics and Space Administration, Goddard Space Flight Center (Mr. Thomas Hennigan, Code 636), Greenbelt, Maryland 20771
- 5 National Aeronautics and Space Administration, Goddard Space Flight Center (Mr. Joseph Sherfey, Code 652), Greenbelt, Maryland 20771
- 6 National Aeronautics and Space Administration, Goddard Space Flight Center (Mr. W. I. Gould, Code 621), Greenbelt, Maryland 20771
- 7 National Aeronautics and Space Administration, (Mr. Ernst M. Cohn, Code RNW), Washington, D. C. 20546
- 8 National Aeronautics and Space Administration, (Mr. James R. Miles, Code SL), Washington, D. C. 20546
- 9 National Aeronautics and Space Administration, (Mr. A. M. Andrus, Code ST), Washington, D. C. 20546
- 10 National Aeronautics and Space Administration, (Mr. Arvin Smith, Code RNW), Washington, D. C. 20546
- 11 National Aeronautics and Space Administration, Goddard Space Flight Center (Office of the Director), Greenbelt, Maryland 20771
- 12-14 National Aeronautics and Space Administration, Goddard Space Flight Center (Office of Assistant Director, Space Science and Satellite Applications), Greenbelt, Maryland 20771
- 15-17 National Aeronautics and Space Administration, Goddard Space Flight Center (Office of Assistant Director, Tracking and Data Systems), Greenbelt, Maryland 20771
- 18-20 National Aeronautics and Space Administration, Goddard Space Flight Center (Office of Technical Services), Greenbelt, Maryland 20771
- 21-22 National Aeronautics and Space Administration, Goddard Space Flight Center (GSFC Library), Greenbelt, Maryland 20771
- 23 National Aeronautics and Space Administration, Goddard Space Flight Center (Contracting Officer, Code 246), Greenbelt, Maryland 20771

- 24-27 National Aeronautics and Space Administration, Goddard Space Flight Center (Technical Information Division, Code 250), Greenbelt, Maryland 20771
- 28-30 National Aeronautics and Space Administration, Scientific and Technical Information Facility, P. O. Box 5700, Bethesda, Maryland 20014
- 31 National Aeronautics and Space Administration, Ames Research Center (Mr. A. S. Hertzog/Mr. J. R. Swain), Moffett Field, California 94035
- 32 National Aeronautics and Space Administration, Langley Research Center (Mr. S. T. Peterson/Mr. Harry Ricker), Langley Station, Hampton, Virginia 23365
- 33 National Aeronautics and Space Administration, Lewis Research Center (Mr. Robert Miller), 21000 Brookpark Road, Cleveland, Ohio 44135
- 34 National Aeronautics and Space Administration, Lewis Research Center (Mr. N. D. Sanders), 21000 Brookpark Road, Cleveland, Ohio 44135
- 35 National Aeronautics and Space Administration, Lewis Research Center (Mr. Robert L. Cummings), 21000 Brookpark Road, Cleveland, Ohio 44135
- 36 National Aeronautics and Space Administration, Manned Space Craft Center (Mr. Richard Ferguson for EP-5), Houston, Texas 77058
- 37 National Aeronautics and Space Administration, Manned Space Craft Center (Mr. Robert Cohen), Houston, Texas 77058
- 38 National Aeronautics and Space Administration, Manned Space Craft Center (Mr. James T. Kennedy), Houston, Texas 77058
- 39 National Aeronautics and Space Administration, Manned Space Craft Center (Mr. Forrest E. Eastman, EE-4), Houston, Texas 77058
- 40 National Aeronautics and Space Administration, Marshall Space Flight Center (Mr. Philip Youngblood), Huntsville, Alabama 35812
- 41 Jet Propulsion Laboratory (Mr. Aiji Uchiyama), 4800 Oak Grove Drive, Pasadena, California 91103
- 42 U. S. Army Engineer R & D Labs. (Electrical Power Branch), Fort Belvoir, Virginia 22060

- 43 U. S. Army Engineer R & D Labs. (Mr. Arthur F. Daniel, Code SELRA/SL-PS), Fort Monmouth, New Jersey 07703
- 44 U. S. Army Materiel Command, Harry Diamond Labs. (Mr. Nathan Kaplan), Room 300, Building 92, Connecticut Avenue & Van Ness Street, N.W., Washington, D. C. 20438
- 45 U. S. Army Materiel Command, Research Division (Mr. John W. Crellin), AMCRD-RSCM T-7, Washington 25, D. C.
- 46 Natick Labs., Clothing & Organic Materials Division (Mr. Leo A. Spano/Mr. Robert N. Walsh), Natick, Massachusetts
- 47 U. S. Army TRECOM, Physical Sciences Group (SMOFE), Ft. Eustice, Virginia 23604
- 48 U. S. Army Reserach Office (Mr. Paul Greer/Dr. Wilhelm Jorgensen), Box CM, Duke Station, Durham, North Carolina
- 49 U. S. Army Mobility Command, Reserach Division (Mr. O. Renius, AMSMO-RR), Center Line, Michigan 48015
- 50 Headquarters, U. S. Army Materiel Command, Development Division (Mr. Marshall D. Aiken, AMCRD-DE-MO-PO), Washington 25, D. C.
- 51 Office of Naval Research (Dr. Ralph Roberts/Mr. H. W. Fox), Department of the Navy, Washington, D. C. 20360
- 52 Chief, Bureau of Naval Weapons (RAAE), Navy Department, Washington, D. C. 20360
- 53 Chief, Bureau of Naval Weapons (FQ-1), Navy Department, Washington, D. C. 20360
- 54 Chief, Bureau of Naval Weapons (RTMS), Navy Department, Washington, D. C. 20360
- 55 Chief, Bureau of Ships (Mr. Bernard B. Rosenbaum, Code 340/Mr. C. G. Viglotti, Code 660), Navy Department, Washington, D. C.
- 56 Commanding Officer, U. S. Naval Ordnance Laboratory (Mr. William C. Spindler, Code 441), Corona, California 91720
- 57 Commander, U. S. Naval Ordnance Laboratory White Oak (Mr. Philip B. Cole, Code WB), Silver Spring, Maryland 20919

- 58 U. S. Naval Reserach Laboratory (Code 6160),
Washington, D. C. 20360
- 59 Wright-Patterson Air Force Base, Aeronautical Systems
Division (Mr. James Elsworth Cooper), Dayton,
Ohio 45433
- 60 AF Cambridge Lab. (Mr. F. X. Doherty/Mr. Edward Raskind),
L. G. Hanscom Field, Bedford, Massachusetts 01731
- 61 Rome Air Development Center, ESD (Mr. F. J. Mollura),
Griffiss Air Force Base, New York 13442
- 62 CAPT William H. Ritchie, Space Systems Division
(SSZAE-11), Air Force Unit Post Office, Los Angeles,
California 90045
- 63 CAPT William Hoover, Air Force Ballistic Missile
Division (WEZYA-21), Air Force Unit Post Office,
Los Angeles, California 90045
- 64 Office of the Deputy Commander AFSC for Aerospace
Systems (Mr. W. J. Bennison), United States Air Force,
Los Angeles, California 90045
- 65 U. S. Atomic Energy Commission, Army Reactors, DRD,
(Mr. Donald B. Hoatson), Washington, D. C. 20545
- 66 Institute for Defense Analyses (Dr. G. Szego/Mr. R.
Hamilton), 400 Army-Navy Drive, Arlington, Virginia 22202
- 67 National Bureau of Standards (Dr. W. J. Hamer),
Washington 25, D. C.
- 68 Power Information Center, University of Pennsylvania,
Moore School Building, 200 South 33rd Street,
Philadelphia, Pennsylvania 19104
- 69 Office of Technical Services, Department of Commerce,
Washington, D. C. 20009
- 70 Mr. R. A. Eades, D.R.S., British Embassy, 3100
Massachusetts Avenue, N.W., Washington, D. C. 20008
- 71 Canadian Joint Staff, Defense Research Member (WASA),
2450 Massachusetts Avenue, N.W., Washington 25, D. C.
- 72-77 Sonotone Corporation, Battery Division (Mr. August
Mundel), Elmsford, New York 10523